

Thermodynamic Properties of $(\text{Ca,Sr})_2\text{RuO}_4$ in Magnetic Fields

J. Baier^{a,*}, T. Zabel^a, M. Kriener^a, P. Steffens^a, O. Schumann^a, O. Friedt^a,
A. Freimuth^a, A. Revcolevschi^b, S. Nakatsuji^c, Y. Maeno^c, T. Lorenz^a, and M. Braden^a

^a*II. Physikalisches Institut, University of Cologne, 50937 Cologne, Germany*

^b*Lab. de Physico-Chimie de l'État Solide, Université Paris-Sud, France*

^c*Department of Physics, Kyoto University, Kyoto 606-8502, Japan*

Abstract

We have studied the influence of a magnetic field on the thermodynamic properties of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ in the intermediate metallic region with tilt and rotational distortions ($0.2 \leq x \leq 0.5$). We find strong and anisotropic thermal expansion anomalies at low temperatures, which are suppressed and even reversed by a magnetic field. The metamagnetic transition of $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ is accompanied by a large magnetostriction. Furthermore, we observe a strong magnetic-field dependence of c_p/T , that can be explained by magnetic fluctuations.

Key words: ruthenates, layered perovskite, specific heat, thermal expansion, heavy fermions, metamagnetism, electronic correlations
PACS: 65.40.-b, 65.40.Ba, 65.40.De, 71.27.+a, 75.30.Kz

The phase diagram of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ possesses a rich spectrum of structural distortions accompanied by changes of the physical properties [1,2,3]. The spin-triplet superconductor Sr_2RuO_4 is driven to the anti-ferromagnetic Mott insulator Ca_2RuO_4 . With decreasing Sr content, the K_2NiF_4 structure of pure Sr_2RuO_4 gets more and more distorted. First, a rotation of the RuO_6 octahedra around the c axis occurs. This rotational distortion comes along with an increase of the low-T susceptibility χ , that is about a factor 200 larger at $x = 0.5$ than that of Sr_2RuO_4 [1]. Below $x = 0.5$ an additional tilt of the octahedra around an in-plane axis occurs [3] and the low-field magnetization at low temperatures is reduced again. In the tilted phase, at $x = 0.2$, a metamagnetic transition at $H_c \simeq 5$ T is observed, leading to a high-field magnetization which exceeds that of $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ [4]. The variation of the low-T specific heat divided by temperature c_p/T as a function of Ca content resembles that of χ . First, c_p/T increases upon Ca-doping and reaches an unusually high value at $x = 0.5$ ($c_p/T \simeq 255$ mJ/mole Ru-K²), that

lies in the range of typical heavy fermion compounds [4]. Upon further increase of the Ca content, c_p/T again decreases and shows a non-monotonous temperature dependence at low temperatures for $x = 0.2$.

Here, we present measurements of the magnetostriction and the magnetic-field dependence of thermal expansion and specific heat of two single crystals, $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ ($x = 0.2$) and $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ ($x = 0.5$), that were grown by a floating zone technique at Kyoto University ($x = 0.2$) and at the Université de Paris Sud ($x = 0.5$). Magnetostriction and thermal expansion were recorded by high-resolution capacitive dilatometry and the specific heat was measured between 300 mK and 60 K by a home-built Nernst calorimeter based on a commercial ³He refrigerator. The measurements were carried out in magnetic fields up to 14 T. $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ exhibits a large magnetostriction with a steep increase around 6 T at the metamagnetic transition at lowest temperatures (see fig.1, left panel). The length change has been recorded parallel to the c axis, in a longitudinal applied field. On the same sample we find an anomalous thermal expansion (see fig.1, right panel). Upon cooling below 25 K, a strong compression of the c axis sets in. This

* Corresponding author

Email address: baier@ph2.uni-koeln.de (J. Baier).

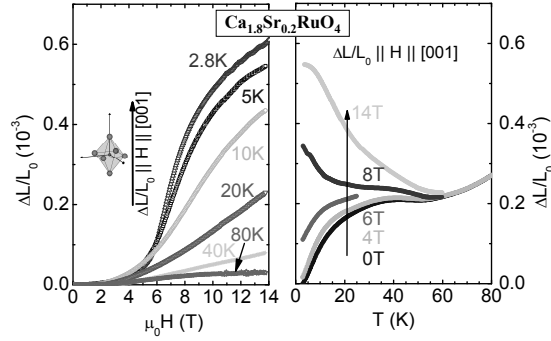


Fig. 1. Magnetostriction (left) and thermal expansion (right) of $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ ($x = 0.2$). The length change was recorded parallel to the c axis in a longitudinal magnetic field.

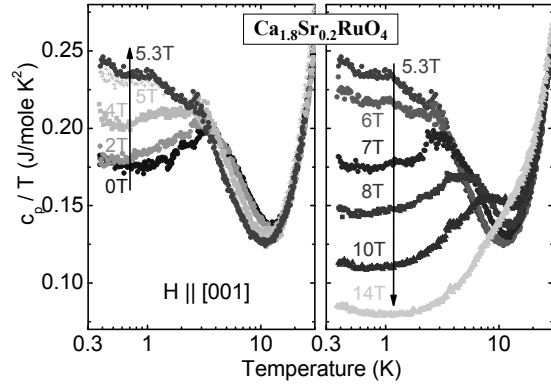


Fig. 2. Specific heat divided by temperature c_p/T of $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ in magnetic fields below (left) and above (right) the critical field of the metamagnetic transition.

anomalous compression is systematically reduced by magnetic fields with $H \leq 6$ T. Above 6 T, this compression turns into a c axis expansion. Measurements of the thermal expansion perpendicular to the c axis (not shown) reveal an opposed behavior, with the ab plane shrinking upon cooling below 25 K [5]. A similar thermal expansion anomaly is also observed beyond the tilted phase for samples with $x = 0.5, 0.62$ and 1, but gets more pronounced with decreasing Sr content [5]. This low-T thermal expansion anomaly and the effect of the magnetic field have to be attributed to an electronic origin. A detailed discussion and the results of neutron diffraction experiments on the same samples have been presented in a previous study [5].

We observe also a strong field-dependence of the low-T specific heat. As mentioned above, without magnetic field, c_p/T is reduced for $x = 0.2$ in comparison with $x = 0.5$. Additionally, it possesses a non-monotonous temperature dependence, with a maximum at about 5 K. As presented in fig. 2, the application of a magnetic field leads first to an increase of the low-T value of c_p/T . At a field of 5.3 T, in the vicinity of the metamagnetic transition, it reaches a maximum value close

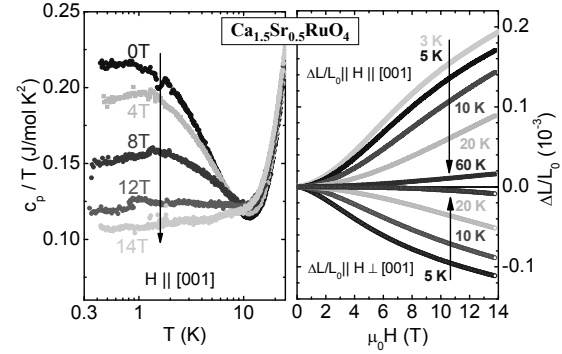


Fig. 3. Left: c_p/T of $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ in magnetic fields applied parallel to the c axis. Right: Magnetostriction of $\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ parallel and perpendicular to the c axis in a longitudinal applied field in each case.

to the c_p/T value for $x = 0.5$ at $H = 0$ T. A further increase of the magnetic field leads again to a decrease of c_p/T . This suggests that the enhancement of c_p/T at the metamagnetic transition is due to magnetic fluctuations that are suppressed by the magnetic field in the spin-polarized phase at $H > H_c$. Recently, it was shown by inelastic neutron scattering experiments on $\text{Ca}_{1.38}\text{Sr}_{0.62}\text{RuO}_4$, that there are strong magnetic fluctuations in this compound [6].

$\text{Ca}_{1.5}\text{Sr}_{0.5}\text{RuO}_4$ shows a qualitatively similar magnetostriction, which, however, is smaller and lacks the steep increase. The c axis expands and the ab plane shrinks in a longitudinal applied magnetic field (see fig. 3, right panel). The specific heat measurements provide a monotonic decrease of c_p/T at low temperatures as a function of magnetic field (see fig. 3, left panel), similar that of $\text{Ca}_{1.8}\text{Sr}_{0.2}\text{RuO}_4$ at $H > H_c$. These findings agree with the idea that the increase of the Sr concentration suppresses the metamagnetic transition field; from $\simeq 5$ T for $x = 0.2$ it goes down close to zero for $x = 0.5$.

In summary, we have found a large magnetostriction and a strong effect of the magnetic field on the low temperature specific heat. These data point to strong magnetic fluctuations around the metamagnetic transition in $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$.

This work was supported by the DFG via SFB 608.

References

- [1] S. Nakatsuji and Y. Maeno, Phys. Rev. Lett. **84**, 2666 (2000).
- [2] S. Nakatsuji and Y. Maeno, Phys. Rev. B **62**, 6458 (2000).
- [3] O. Friedt *et al.*, Phys. Rev. B **63**, 174432 (2001).
- [4] S. Nakatsuji *et al.*, Phys. Rev. Lett. **90**, 137202 (2003).
- [5] M. Kriener *et al.*, cond-mat **0408015**, (2004).

- [6] O. Friedt *et al.*, Phys. Rev. Lett. **93**, 147404 (2004).